

Produktdatenblatt (DE)

Thermoplastisches Polyurethan (TPU),
Polyether-basiert

NORDFLEX® TPU T 90-A

Produktbeschreibung:

NORDFLEX® TPU T 90-A ist ein halogenfreies, Polyether-basiert thermoplastisches Polyurethan (TPU), das sowohl für Extrusions- als auch für Spritzgießanwendungen ausgelegt ist. Das Material zeichnet sich durch eine hervorragende mechanische Festigkeit und eine ausgezeichnete Abriebfestigkeit aus. Darüber hinaus bietet es eine sehr gute Beständigkeit gegenüber Ölen, Fetten und vielen Lösungsmitteln. Aufgrund seiner chemischen Basis als Polyether-basiert ist bei diesem Material jedoch auf eine begrenzte Beständigkeit gegen Hydrolyse und mikrobiellen Abbau zu achten, weshalb eine sorgfältige Vortrocknung vor der Verarbeitung zwingend erforderlich ist.

Eigenschaft	Einheit	Wert	Norm
Härte (nach 3 s)	Shore A	90 ±3 %	ISO 7619
Bruchdehnung		650 ±15 %	ISO 527
Farbe		Natur	
100 % Dehnung	MPa	45 ±15 %	ISO 527
Dichte	g/cm³	1,13 ±2 %	ISO 1183
Abriebverlust	mm³	30 ±15 %	ISO 4649
MFI [190°C / 2.16kg]	g/10min	9.0 ±20 %	ISO 1133

Verarbeitung:

Parameter (Extrusion)	Wert °C
Feed Zone:	175 - 185
Barrel:	185 - 205
Die Head:	200 - 210
Nozzle:	200 - 215

Gesundheits- und Sicherheitshinweise:

Vor der Verarbeitung dieses Materials ist sicherzustellen, dass alle beteiligten Personen über die notwendigen Sicherheitsmaßnahmen informiert sind. Maßgeblich sind die Angaben im jeweiligen Sicherheitsdatenblatt (MSDS), das vom Hersteller bereitgestellt wird.

Lieferform und Lagerung:

NORDFLEX® TPU T 90-A wird in Säcken, BigBags oder Octabins geliefert.

Die erwartete Mindestlagerfähigkeit beträgt 12 Monate ab Versanddatum, sofern das Material trocken, kühl und in der originalen Herstellerpackung gelagert wird.

Die in diesem Dokument enthaltenen Angaben entsprechen dem aktuellen Kenntnisstand zum Zeitpunkt der Veröffentlichung. Sie stellen keine zugesicherte Eigenschaft oder Garantie dar. Die Eignung des Produkts für den jeweiligen Einsatzzweck ist vom Anwender eigenverantwortlich zu prüfen. Es wird keine Haftung für mögliche Schutzrechtsverletzungen übernommen.

Product Data Sheet (EN)

Thermoplastic Polyurethane (TPU),

polyether-based

NORDFLEX® TPU T 90-A

Product Description:

NORDFLEX® TPU T 90-A is a halogen-free, polyether-based thermoplastic polyurethane (TPU) designed for both extrusion and injection molding applications. The material is characterized by excellent mechanical strength and outstanding abrasion resistance. In addition, it offers very good resistance to oils, greases, and many solvents. Due to its chemical base as a polyether-based TPU, this material has limited resistance to hydrolysis and microbial degradation; therefore, careful pre-drying prior to processing is essential.

Property	Unit	Value	Standard
Hardness (after 3 s)	Shore A	90 ±3 %	ISO 7619
Elongation at Break		650 ±15 %	ISO 527
Color		Natur	
Tensile Strength (100 % Elongation)	MPa	45 ±15 %	ISO 527
Density	g/cm³	1,13 ±2 %	ISO 1183
Abrasion Loss	mm³	30 ±15 %	ISO 4649
MFI [190°C / 2.16kg]	g/10min	9.0 ±20 %	ISO 1133

Processing:

Parameter (Extrusion)	Wert °C
Feed Zone:	175 - 185
Barrel:	185 - 205
Die Head:	200 - 210
Nozzle:	200 - 215

Health and Safety Information: Before processing this material, it must be ensured that all involved personnel are informed about the necessary safety precautions. The information provided in the relevant Material Safety Data Sheet (MSDS) supplied by the manufacturer shall apply.

Packaging and Storage:

NORDFLEX® TPU T 90-A is supplied in bags, big bags, or octabins. The expected minimum shelf life is 12 months from the date of shipment, provided that the material is stored dry, cool, and in the original manufacturer's packaging.

The information contained in this document corresponds to the current state of knowledge at the time of publication. It does not constitute a guaranteed property or warranty. The suitability of the product for the respective application must be verified by the user at their own responsibility. No liability is assumed for possible infringements of industrial property rights.

LABORBERICHT / MATERIALMUSTER

Firma: PlastoNord GmbH
Datum der Prüfung: 01.06.2026
Prüfverantwortlicher: N.B.

1. Allgemeine Materialdaten

Materialtyp: TPU

Charge (Batch-Nr.): 2839545556

Farbe: Natur

2. Shore-Härte


Shore-Härte A: 88 ±3

Shore-Härte D: 28 ±2


3. Schmelzindex (MFI) - ISO 1133

MFI [190°C / 2.16 kg]: 9.0 g/10 min

4. Spektrometer-Analyse

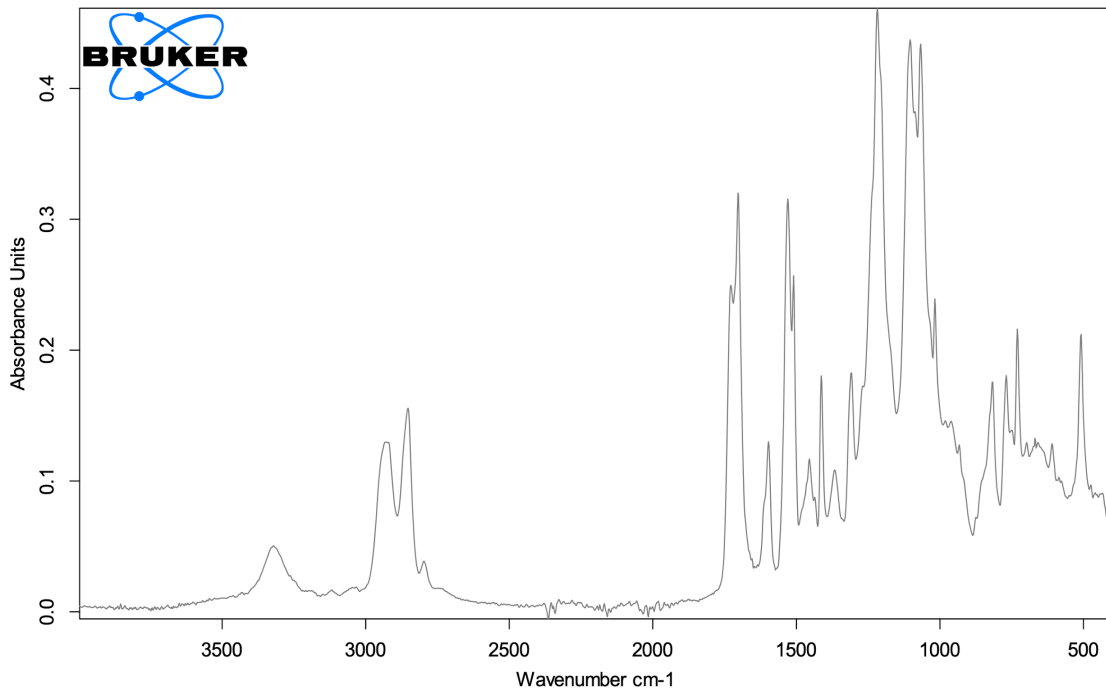

Die FT-IR-spektroskopische Untersuchung der Probe NORDFLEX TPU 88-A CH-2839545556 bestätigt ein thermoplastisches Polyurethan (TPU) mit überwiegend polyetherbasierter Struktur. Charakteristische Absorptionsbanden im Bereich von ca. 3300 cm^{-1} (N-H), $1700\text{--}1720\text{ cm}^{-1}$ (Urethan-Carbonylgruppen) sowie die ausgeprägten Etherbanden im Bereich von $1100\text{--}1000\text{ cm}^{-1}$ entsprechen dem typischen Spektrum eines polyetherbasierten TPU. Zusätzlich sind übliche Verarbeitungs- und Stabilisierungsadditive vorhanden. Hinweise auf relevante Fremdpolymere, erhöhte Füllstoffgehalte oder Flammenschutzsysteme wurden nicht festgestellt. Die Probe ist als polyetherbasiertes TPU-Compound zu bewerten.

Unterschrift Prüfer: 

Datum: 01.06.2026

LAB REPORT / MATERIAL SAMPLES

Company: PlastoNord GmbH
Date of Testing: 01.06.2026
Responsible Inspector: N.B.

1. General Material Information

Material Type: TPU
Batch Number: 2839545556
Color: Natur


2. Shore Hardness

Shore Hardness A: 88 ±3
Shore Hardness D: 28 ±2

3. Melt Flow Index (MFI) - ISO 1133

MFI [190°C / 21.6 kg]: 9.0 g/10 min

4. Spectrometer Analysis

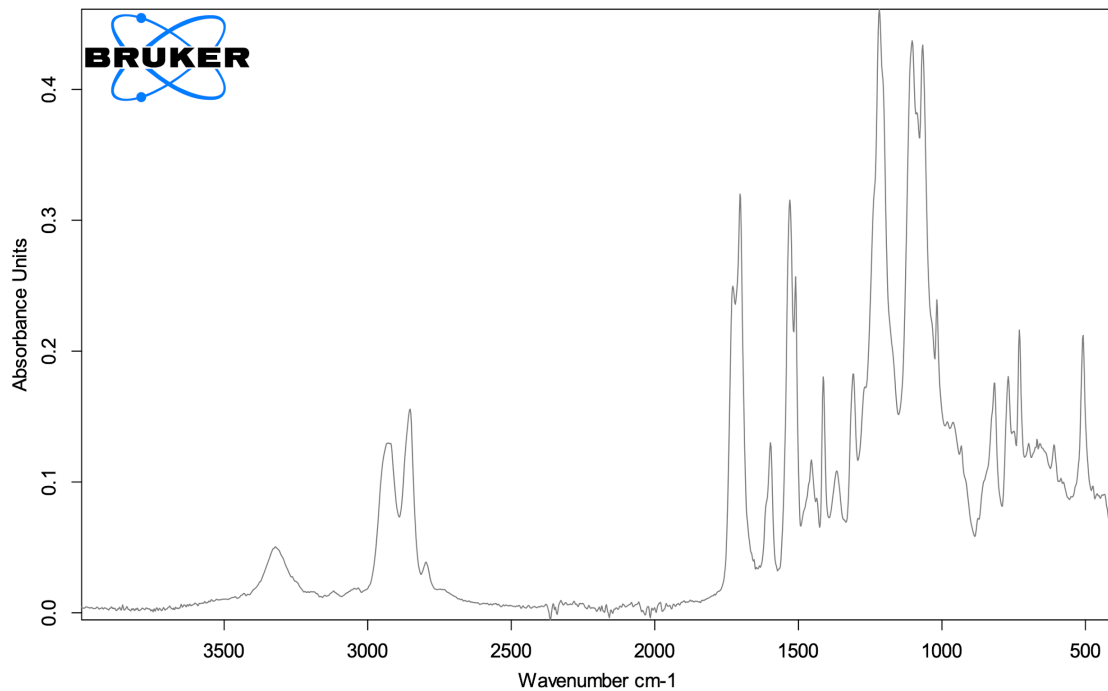

The FT-IR spectroscopic analysis of CH-2839545556 confirms a thermoplastic polyurethane (TPU) with a predominantly polyether-based structure. Characteristic absorption bands at approximately 3300 cm^{-1} (N-H), $1700\text{--}1720\text{ cm}^{-1}$ (urethane carbonyl groups), and the pronounced ether-related bands within $1100\text{--}1000\text{ cm}^{-1}$ correspond to the typical fingerprint of a polyether-based TPU. Common processing and stabilization additives are also present. No indications of significant foreign polymers, elevated filler contents, or flame-retardant systems were detected. The sample is therefore classified as a polyether-based TPU compound.

Inspector Signature: 

Date: 01.06.2026